

DIN EN 10305-5



ICS 77.140.75

Supersedes
DIN EN 10305-5:2003-08

**Steel tubes for precision applications –
Technical delivery conditions –
Part 5: Welded cold sized square and rectangular tubes
English translation of DIN EN 10305-5:2010-05**

Präzisionsstahlrohre –
Technische Lieferbedingungen –
Teil 5: Geschweißte maßumgeformte Rohre mit quadratischem und rechteckigem
Querschnitt
Englische Übersetzung von DIN EN 10305-5:2010-05

Tubes de précision en acier –
Conditions techniques de livraison –
Partie 5: Tubes soudés calibrés avec section carrée et rectangulaire
Traduction anglaise de DIN EN 10305-5:2010-05

Document comprises 24 pages

Translation by DIN-Sprachendienst.

In case of doubt, the German-language original shall be considered authoritative.

A comma is used as the decimal marker.

National foreword

This standard has been prepared by Technical Committee ECISS/TC 29 "Steel tubes and fittings for steel tubes" (Secretariat: UNI, Italy), SC 11 "Tubes for mechanical and general engineering purposes" (Secretariat: AFNOR, France).

The responsible German body involved in its preparation was the *Normenausschuss Eisen und Stahl* (Steel and Iron Standards Committee), Working Committee NA 021-00-09-09 UA *Präzisionsstahlrohre*.

This European Standard specifies technical delivery conditions for welded cold sized square and rectangular tubes which are characterized by having precisely defined tolerances on dimensions, a specified surface roughness and defined mechanical properties.

Amendments

This standard differs from DIN EN 10305-5:2003-08 as follows:

- a) Suitability for hot-dip galvanizing has been specified as an option.
- b) The standard has been editorially revised.

Previous editions

DIN 2393-1: 1981-08, 1994-09

DIN 2393-2: 1981-08, 1994-09

DIN EN 10305-5: 2003-08

English Version

**Steel tubes for precision applications - Technical delivery
conditions - Part 5: Welded cold sized square and rectangular
tubes**

Tubes de précision en acier - Conditions techniques de
livraison - Partie 5 : Tubes soudés calibrés avec section
carrée et rectangulaire

Präzisionsstahlrohre - Technische Lieferbedingungen - Teil
5: Geschweißte maßumgeformte Rohre mit quadratischem
und rechteckigem Querschnitt

This European Standard was approved by CEN on 22 November 2009.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	5
4 Symbols	5
5 Classification and designation.....	5
5.1 Classification.....	5
5.2 Designation	5
6 Information to be supplied by the purchaser	6
6.1 Mandatory information	6
6.2 Options	6
6.3 Example of an order	7
7 Manufacturing process	7
7.1 Steelmaking process	7
7.2 Tube manufacture and delivery conditions	7
8 Requirements	8
8.1 General.....	8
8.2 Chemical composition	8
8.3 Mechanical properties.....	9
8.4 Appearance and internal soundness.....	10
8.5 Dimensions and tolerances	11
9 Inspection	17
9.1 Types of inspection	17
9.2 Inspection documents.....	17
9.3 Summary of inspection and testing.....	18
10 Sampling	18
10.1 Frequency of tests	18
10.2 Preparation of samples and test pieces.....	18
11 Test methods.....	19
11.1 Tensile test	19
11.2 Dimensional inspection	19
11.3 Roughness measurement.....	20
11.4 Visual examination	20
11.5 Non-destructive testing.....	20
11.6 Retests, sorting and reprocessing.....	20
12 Marking	20
13 Protection and packaging.....	20
Bibliography	22

Foreword

This document (EN 10305-5:2010) has been prepared by Technical Committee ECISS/TC 110 “Steel tubes, and iron and steel fittings”, the secretariat of which is held by UNI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by July 2010, and conflicting national standards shall be withdrawn at the latest by July 2010.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 10305-5:2003.

EN 10305, *Steel tubes for precision applications — Technical delivery conditions*, consists of the following parts:

- *Part 1: Seamless cold drawn tubes*
- *Part 2: Welded cold drawn tubes*
- *Part 3: Welded cold sized tubes*
- *Part 4: Seamless cold drawn tubes for hydraulic and pneumatic power systems*
- *Part 5: Welded cold sized square and rectangular tubes*
- *Part 6: Welded cold drawn tubes for hydraulic and pneumatic power systems*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

This European Standard specifies the technical delivery conditions for welded cold sized steel tubes of square and rectangular cross section for precision applications.

Tubes according to this document are characterised by having precisely defined tolerances on dimension and a specified maximum surface roughness. Typical fields of application are in the automotive, furniture and general engineering industries.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 10020:2000, *Definition and classification of grades of steel*

EN 10021:2006, *General technical delivery conditions for steel products*

EN 10027-1, *Designation systems for steels — Part 1: Steel names*

EN 10027-2, *Designation systems for steels — Part 2: Numerical system*

EN 10052:1993, *Vocabulary of heat treatment terms for ferrous products*

EN 10168, *Steel products — Inspection documents — List of information and description*

EN 10204, *Metallic products — Types of inspection documents*

EN 10246-3¹⁾, *Non-destructive testing of steel tubes — Part 3: Automatic eddy current testing of seamless and welded (except submerged arc-welded) steel tubes for the detection of imperfections*

EN 10246-8²⁾, *Non-destructive testing of steel tubes — Part 8: Automatic ultrasonic testing of the weld seam of electric welded steel tubes for the detection of longitudinal imperfections*

EN 10256, *Non-destructive testing of steel tubes — Qualification and competence of level 1 and 2 non-destructive testing personnel*

EN 10266:2003, *Steel tubes, fittings and structural hollow sections — Symbols and definitions of terms for use in product standards*

EN ISO 377, *Steel and steel products — Location and preparation of samples and test pieces for mechanical testing (ISO 377:1997)*

EN ISO 2566-1, *Steel — Conversion of elongation values — Part 1: Carbon and low alloy steels (ISO 2566-1:1984)*

EN ISO 4287, *Geometrical product specifications (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters (ISO 4287:1997)*

1) Under revision to become EN ISO 10893-2, *Non-destructive testing of steel tubes — Part 2: Automated eddy current testing of seamless and welded (except submerged arc-welded) steel tubes for the detection of imperfections (ISO/DIS 10893-2:2009)*.

2) Under revision to become EN ISO 10893-11, *Non-destructive testing of steel tubes — Part 11: Automated ultrasonic testing of weld seam of welded steel tubes for the detection of longitudinal and/or transversal imperfections (ISO/DIS 10893-11:2009)*.

EN ISO 6892-1, *Metallic materials — Tensile testing — Part 1: Method of test at room temperature (ISO 6892-1:2009)*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 10020:2000, EN 10021:2006, EN 10052:1993, EN 10266:2003 and the following apply.

3.1

employer

organization for which a person works on a regular basis

NOTE The employer can be either the tube manufacturer or a third party organization providing non-destructive testing (NDT) services.

3.2

manufacturer

party to produce and to deliver tubes in accordance with this document

NOTE Where tubes are delivered by a supplier, see EN 10021:2006, Clause 6.

3.3

imperfection

discontinuity in the wall or on the pipe surfaces detectable by methods described in this document

NOTE Imperfections with a size complying with the acceptance criteria specified in this document are considered to have no practical implication on the intended use of the product.

3.4

defect

imperfection of a size not complying with the acceptance criteria specified in this document

NOTE Defects are considered to adversely affect or limit the intended use of the product.

3.5

parent coil

coil originating from the hot rolling process prior to any further operation (pickling, slitting, cold rolling or coating)

4 Symbols

For the purposes of this document, the symbols in EN 10266:2003 apply.

5 Classification and designation

5.1 Classification

In accordance with the classification system in EN 10020 the steel grades given in Table 2 are non-alloy quality steels.

5.2 Designation

For the tubes covered by this document the steel designation consists of the number of this document (EN 10305-5) plus either:

- a) the steel name in accordance with EN 10027-1; or
- b) the steel number in accordance with EN 10027-2.

6 Information to be supplied by the purchaser

6.1 Mandatory information

The following information shall be supplied by the purchaser at the time of enquiry and order:

- a) the quantity (mass or total length or number of pieces);
- b) the term "tube";
- c) the dimensions (see 8.5.1);
- d) the steel designation (see 5.2);
- e) the delivery condition including the surface condition (see 7.2.1 and 7.2.2).

6.2 Options

A number of options are specified in this document and these are listed below. In the event that the purchaser does not indicate a wish to implement any of these options at the time of enquiry and order, the tubes shall be supplied in accordance with the basic specification (see 6.1).

- 1) specification of a steel grade not specified in this document (see 8.2);
- 2) suitability for hot-dip galvanizing (see 8.2);
- 3) surface condition for further processing (see 8.4.1);
- 4) position of the weld line (see 8.4.2);
- 5) removal of internal weld bead (see 8.4.3);
- 6) measurement of surface roughness (see 8.4.5);
- 7) specific surface roughness (see 8.4.5);
- 8) non-destructive testing of the weld seam for the detection of longitudinal imperfections (see 8.4.8);
- 9) reduced wall thickness tolerance (see 8.5.3);
- 10) unilateral wall thickness tolerance (see 8.5.3);
- 11) exact length (see 8.5.5);
- 12) another specified length and/or tolerance (see 8.5.5);
- 13) reduced maximum deviation from straightness (see 8.5.6);
- 14) specified end finishing (see 8.5.10);
- 15) inspection certificate 3.1 (see 9.1 and 9.2.1);

- 16) test unit with tubes from one cast only (see 10.1.1);
- 17) alternative marking (see Clause 12);
- 18) delivery without corrosion protection (see Clause 13);
- 19) specified corrosion protection (see Clause 13);
- 20) unbundled tubes or specific method of packaging (see Clause 13).

6.3 Example of an order

12 000 m tube, size 50 mm × 30 mm with a wall thickness of 3 mm in accordance with EN 10305-5, made of steel grade E235 in the normalized condition with strip surface condition S2 (pickled) with a 3.1 inspection certificate in accordance with EN 10204:

12 000 m tubes – 50 × 30 × 3 – EN 10305-5 – E235+N – S2 – Option 15

7 Manufacturing process

7.1 Steelmaking process

The steelmaking process is at the discretion of the manufacturer with the exception that the open hearth (Siemens-Martin) process shall not be employed unless in combination with a secondary steelmaking or ladle refining process.

Steels shall be fully killed.

NOTE This excludes the use of rimming, balanced or semi-killed steel.

7.2 Tube manufacture and delivery conditions

7.2.1 The tubes shall be manufactured from strip by electric welding. The tubes shall not contain strip end welds except for tubes to be supplied coiled for which the delivery conditions +A or +N can be specified.

Possible surface conditions are:

- a) S1 (black);
- b) S2 (pickled);
- c) S3 (cold rolled);
- d) S4 (coated to an agreed condition).

NOTE The surface conditions S1 and S3 apply for the strip. The surface condition S2 and S4 can apply for the strip or the tube; the purchaser should, where necessary, indicate the required condition at the time of enquiry and order.

7.2.2 Tubes made of the steel grades E155, E195, E235, E275 and E355 shall be supplied in one of the delivery conditions given in Table 1, except +CR2.

Tubes made of the grades E190, E220, E260, E320, E370 and E420 shall be supplied in the delivery condition +CR2.

7.2.3 All non-destructive testing (NDT) activities shall be carried out by qualified and competent level 1, 2 and/or 3 personnel authorised to operate by the employer.

The qualification shall be in accordance with EN 10256 or, at least, an equivalent to it.

It is recommended that the level 3 personnel be certified in accordance with EN 473, or, at least, an equivalent to it.

The operation authorisation issued by the employer shall be in accordance with a written procedure. NDT operations shall be authorised by a level 3 NDT individual approved by the employer.

NOTE The definition of level 1, 2 and 3 can be found in appropriate standards, e.g. EN 473 and EN 10256.

Table 1 — Delivery conditions

Designation	Symbol ^a	Description
Welded and cold sized	+CR1	Normally not heat treated, but suitable for final annealing. ^b
	+CR2	Not intended for heat treatment after the welding and sizing process. ^c
Soft annealed	+A	After welding and sizing the tubes are annealed in a controlled atmosphere.
Normalized	+N	After welding and sizing the tubes are normalized in a controlled atmosphere.
^a In accordance with EN 10027-1. ^b After annealing or normalizing, the resulting mechanical properties meet the requirements specified in Table 4 for the delivery condition +A or +N, respectively are normally obtained. ^c If further heat treatment is applied, the resulting mechanical properties may be outside the specified requirements.		

8 Requirements

8.1 General

The tubes, when supplied in a delivery condition indicated in Table 1 and inspected in accordance with Clauses 9, 10 and 11, shall comply with the requirements of this document.

In addition the general technical delivery requirements specified in EN 10021 apply.

8.2 Chemical composition

The cast analysis reported by the steel producer shall apply and comply with the requirements of Table 2. A steel grade not specified in this document may be specified (see option 1).

Option 1: A steel grade not specified in this document with a maximum total content of alloying elements of 5 % and agreed chemical composition, mechanical properties and delivery condition, is specified.

NOTE When subsequently welding tubes produced according to this document, account should be taken of the fact that the behaviour of the steel during and after welding is dependent not only on the steel composition, but also on the conditions of preparing for and carrying out the welding.

Option 2: The composition of the specified steel grade shall be such that it is suitable for hot-dip galvanizing (see e.g. EN ISO 1461 for guidance).

Table 2 — Chemical composition (cast analysis)^a

Steel grade		% by mass					
Steel name	Steel number	C max.	Si max.	Mn max.	P max.	S max.	Al _{total} ^b min.
E155	1.0033	0,11	0,35	0,70	0,025	0,025	0, 015
E190	1.0031	0,10					
E195	1.0034	0,15	0,35	0,70	0,025	0,025	0, 015
E220	1.0215	0,14					
E235	1.0308	0,17	0,35	1,20	0,025	0,025	0, 015
E260	1.0220	0,16					
E275	1.0225	0,21	0,35	1,40	0,025	0,025	0, 015
E320	1.0237	0,20					
E355	1.0580	0,22	0,55	1,60	0,025	0,025	0,020
E370	1.0261	0,21					
E420	1.0575	0,16	0,50	1,70	0,025	0,025	0,020

^a Elements not included in this table (but see footnote ^b) shall not be intentionally added to the steel without the agreement of the purchaser, except for elements which may be added for the purposes of deoxidation and/or nitrogen binding. All appropriate measures shall be taken to prevent the addition of undesirable elements from scrap or other materials used in the steel making process.

^b This requirement is not applicable provided the steel contains a sufficient amount of other nitrogen binding elements, such as Ti, Nb or V. When using titanium, the manufacturer shall verify that $(Al + Ti/2) \geq 0,020$. Additions of Nb, Ti and V are permitted at the discretion of the manufacturer. The content of these elements shall be reported.

Table 3 specifies the permissible deviations of product analysis from the specified limits on cast analysis given in Table 2.

Table 3 — Permissible deviations of the product analysis from the specified limits given in Table 2

Element	Specified limit of the cast analysis % by mass	Permissible deviation of the product analysis % by mass
C	≤ 0,22	+ 0,02
Si	≤ 0,55	+ 0,05
Mn	≤ 1,70	+ 0,10
P	≤ 0,025	+ 0,005
S	≤ 0,025	+ 0,005
Al	≥ 0,015	- 0,005

8.3 Mechanical properties

The mechanical properties of the tubes covered by this document shall conform to the requirements of Table 4 or 5.

NOTE Subsequent processing (cold or hot) can change the mechanical properties.

Table 4 — Mechanical properties at room temperature for the delivery conditions +CR1, +A and +N

Steel grade		Minimum values for the delivery condition ^{a, b}						
		+CR1		+A		+N		
Name	Number	R_m^c MPa	A %	R_m MPa	A %	R_m MPa	R_{eH} MPa	A %
E155	1.0033	290	15	260	28	270 to 410	155	28
E195	1.0034	330	8	290	28	300 to 440	195	28
E235	1.0308	390	7	315	25	340 to 480	235	25
E275	1.0225	440	6	390	22	410 to 550	275	22
E355	1.0580	540	5	450	22	490 to 630	355	22

NOTE The mechanical properties and technological properties of the weld zone may, in the case of the delivery conditions +CR1 and +A, differ from those of the base material.

^a R_m : tensile strength; R_{eH} : upper yield strength (but see 11.1); A : elongation after fracture. For symbols for the delivery condition see Table 1.

^b 1 MPa = 1 N/mm².

^c Depending on the degree of cold forming the strip material and sizing the as welded tube, the yield strength may nearly be as high as the tensile strength. For calculation purposes yield strength values of $R_{eH} \geq 0,7 R_m$ are recommended in the +CR1 condition.

Table 5 — Mechanical properties (minimum values) at room temperature for the delivery condition +CR 2^{a, b}

Steel grade		Tensile strength	Yield strength	Elongation after fracture
Name	Number	R_m MPa	R_{eH} MPa	A %
E190	1.0031	270	190	26
E220	1.0215	310	220	23
E260	1.0220	340	260	21
E320	1.0237	410	320	19
E370	1.0261	450	370	15
E420	1.0575	490	420	12

NOTE The mechanical and technological properties of the weld zone may differ from those of the base material.

^a For the symbol for the delivery condition see Table 1.

^b 1 MPa = 1 N/mm².

8.4 Appearance and internal soundness

8.4.1 The internal and external surface finish of the tubes shall be typical of the manufacturing process and, where applicable, the heat treatment employed.

Option 3: A surface condition suitable for special further processing is specified by the purchaser.

Normally, the finish and surface condition shall be such that any surface imperfections requiring dressing can be identified. Any surface imperfections, which in accordance with the manufacturer's experience might be considered defects as specified in 8.4.6, shall be dressed in accordance with 8.4.7, or the tube or part of tube shall be rejected.

8.4.2 The position of the weld line is at the discretion of the manufacturer, unless option 4 is specified.

Option 4: The position of the weld line, a) or b) or c) or d), is specified by the purchaser. The deviation of the weld line from a specified position shall be:

- a) narrow side (from the centre line): $\pm 10\%$ of side length or $\pm 3\text{ mm}$ whichever is the greater;
- b) wide side (from the centre line): $\pm 10\%$ of side length or $\pm 3\text{ mm}$ whichever is the greater;
- c) corner: the weld shall be within the corner radius defined by C_1 and C_2 (see Figure 1);
- d) any other position: agreed tolerance.

8.4.3 The external weld bead shall be removed flush with the surface. The height of the internal weld is not limited, unless option 5 is specified.

Option 5: The height of the internal weld bead shall not exceed a specified value or be removed.

The wall thickness in the weld area shall not be lower than the specified minimum wall thickness.

8.4.4 Outside the weld area, the roughness on the outside surface shall be: $Ra \leq 4\text{ }\mu\text{m}$.

8.4.5 Verification of surface roughness and/or improved levels of roughness may be specified (see options 6 and 7).

Option 6: The surface roughness shall be measured in accordance with 11.3 and reported.

Option 7: A specific surface roughness of agreed type and limiting value is specified. The roughness shall be measured and reported.

8.4.6 Surface imperfections which encroach on the specified minimum wall thickness shall be considered defects and tubes containing these shall be deemed not to conform to this document.

8.4.7 It shall be permissible to dress, only by grinding or machining, surface imperfections provided that, after doing so, the wall thickness in the dressed area is not less than the specified minimum wall thickness. All dressed areas shall blend smoothly into the contour of the tube.

8.4.8 Verification of internal soundness of the welded zone by non-destructive testing may be specified by the purchaser (see option 8).

Option 8: Non-destructive testing of the weld seam for the detection of longitudinal imperfections in accordance with 11.5 is specified.

8.4.9 Tubes in the delivery condition +A or +N shall be free of loose scale but may show discoloration.

8.5 Dimensions and tolerances

8.5.1 Side length(s), wall thickness and mass per unit length

8.5.1.1 The tubes shall be specified by side length(s) and wall thickness.

8.5.1.2 Preferred sizes and tolerances are given in Table 6.

8.5.1.3 For the specified sizes the masses per unit length are given in Table 6. For other sizes the mass per unit length may be calculated using the formula

$$M = 0,785 A, \text{ in kilograms per metre (kg/m)} \quad (1)$$

where

M is the mass per unit length;

A is the cross-sectional area in square centimetres (cm²).

For calculation of A Equation (2) or (3) applies:

a) for wall thicknesses $\leq 2,5$ mm,

$$A = \frac{2T(B + H - 2T) - (4 - \pi)(0,5T)^2}{10^2} \quad (2)$$

b) for wall thicknesses $> 2,5$ mm,

$$A = \frac{2T(B + H - 2T) - (4 - \pi) \left((1,75T)^2 - (0,75T)^2 \right)}{10^2} \quad (3)$$

8.5.2 Side length(s) tolerances

For the delivery conditions +CR1 and +CR2 the tolerances given in Table 6 apply. For intermediate sizes the tolerances of the next greater sizes shall apply.

For the delivery conditions +A and +N the tolerances shall be agreed at the time of enquiry and order.

Table 6 — Sizes, tolerances and mass per unit length

Dimensions in millimetres

Side length(s)			Mass per unit length in kg/m ^a for specified thickness <i>T</i>						
<i>H</i>	<i>B</i> (or <i>H</i>)	Tolerance of <i>H</i> and <i>B</i>	1	1,25	1,5	2	2,5	3	4
15	15	± 0,20	0,438	0,537	0,632	0,810			
20	10 15 20	± 0,20	0,438 0,516 0,595	0,537 0,635 0,733	0,632 0,750 0,868	0,810 0,967 1,12			
25	15 25	± 0,25	0,595 0,752	0,733 0,930	0,868 1,10	1,12 1,44			
30	10 15 20 30	± 0,25	0,595 0,673 0,752 0,909	0,733 0,831 0,930 1,13	0,868 0,985 1,10 1,34	1,12 1,28 1,44 1,75			
34	20	± 0,25	0,815	1,01	1,20	1,56	2,15	2,39	
35	20 25 35	± 0,25	0,830 0,909 1,07	1,03 1,13 1,32	1,22 1,34 1,57	1,59 1,75 2,07	1,95 2,15 2,54	2,39 2,86	
40	20 25 30 40	± 0,30			1,34 1,46 1,57 1,81	1,75 1,91 2,07 2,38	2,15 2,34 2,54 2,93	2,39 2,63 2,86 3,33	4,25
45	45	± 0,30			2,05	2,69	3,33	3,80	4,88
50	20 25 30 40 50	± 0,30			1,57 1,69 1,81 2,05 2,28	2,07 2,22 2,38 2,69 3,01	2,54 2,74 2,93 3,33 3,72	2,86 3,10 3,33 3,80 4,28	4,25 4,88 5,51
60	20 30 40 50 60	± 0,35				2,38 2,69 3,01 3,32 3,64	2,93 3,33 3,72 4,11 4,50	3,33 3,80 4,28 4,75 5,22	4,88 5,51 6,14 6,76
70	40 70	± 0,40				3,32 4,26	4,11 5,29	4,75 6,16	6,14 8,02
80	20 30 40 50 60 80	± 0,50				3,01 3,32 3,64 3,95 4,26 4,89	3,72 4,11 4,50 4,90 5,29 6,07	4,28 4,75 5,22 5,69 6,16 7,10	6,76 7,39 8,02 9,28
90	90	± 0,60				5,52	6,86	8,04	10,5
100	40 50 60 80 100	± 0,65				4,26 4,58 4,89 5,52 6,15	5,29 5,68 6,07 6,86 7,64	6,16 6,63 7,10 8,04 8,99	8,02 8,65 9,28 10,5 11,8
120	40 60	± 0,70				4,89 5,52	6,07 6,86	7,10 8,04	9,28 10,5

NOTE The tubes are normally available in sizes for which masses per unit length are specified. However, other sizes (including other wall thicknesses) may be ordered.


^a The specified masses per unit length are based on a density of 7,85 kg/dm³ and on specified dimensions for the following external corner radii: $T \leq 2,5$ mm: 0,5*T*; $T = 3$ mm to 4 mm: 1,75 *T*.

8.5.3 Wall thickness tolerances

Depending on the wall thickness T , the following tolerances are specified:

- a) $T \leq 1,5 \text{ mm}$: $\pm 0,15 \text{ mm}$;
- b) $T > 1,5 \text{ mm}$: $\pm 0,1 T \text{ mm}$ or $\pm 0,35 \text{ mm}$, whichever is the smaller.

The plus tolerance does not apply to the weld area or the dimensions $C_1 + 5 \text{ mm}$ and $C_2 + 5 \text{ mm}$ in the corner region (see Figure 1).

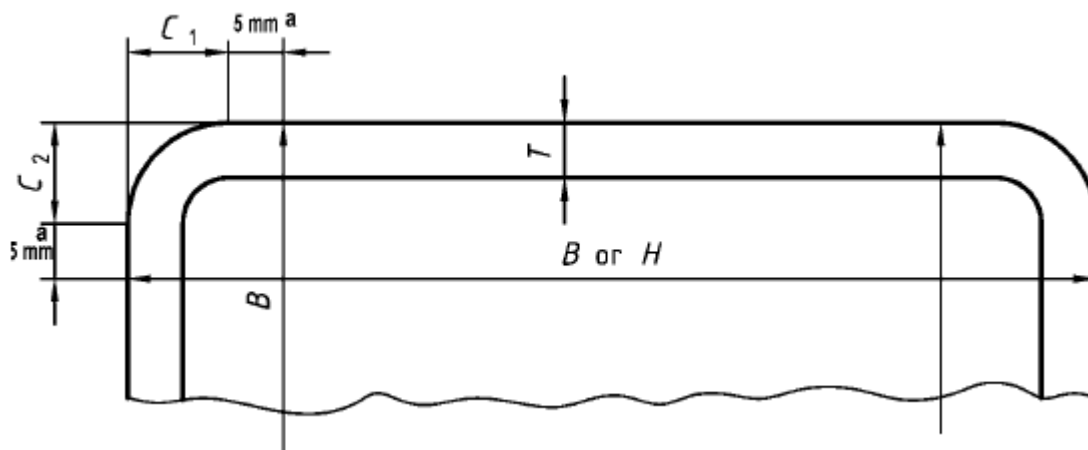

Key

- a minimum distance to C_1 and C_2 when measuring T , and maximum distance when measuring B or H
- C_1, C_2 external corner radii
- B side length (broad)
- H side length (height)
- T wall thickness

Figure 1 — Limiting cross-sectional positions for measuring the dimensions B , H and T

Other wall thickness tolerances may be specified (see option 9 and 10).

Option 9: A reduced wall thickness tolerance shall be applied. The value shall be agreed at the time of enquiry and order.

Option 10: A unilateral wall thickness tolerance is specified, with the tolerance range specified in 8.5.3, first paragraph.

8.5.4 Corner profile

The lengths C_1 and C_2 shall not exceed $1,5 T$ for wall thicknesses $\leq 2,5 \text{ mm}$ and $2,2 T$ for wall thicknesses $2,5 \text{ mm} < T \leq 4 \text{ mm}$.

NOTE The static and dynamic properties of square and rectangular tubes with sharp corners cannot always be achieved.

8.5.5 Length and length tolerances

Unless option 11 or 12 is specified the tubes shall be delivered in standard lengths of 6 m with a tolerance of $+100$
 0 mm.

Option 11: An exact length with tolerances as given in Table 7 is specified. For lengths ≤ 500 mm or $> 8\,000$ mm a specified unilateral tolerance applies.

Table 7 — Tolerances for exact lengths

Length L mm	Tolerance mm
≤ 500	+ by agreement 0^a
$500 < L \leq 2\,000$	+ 3 0
$2\,000 < L \leq 5\,000$	+ 5 0
$5\,000 < L \leq 8\,000$	+ 10 0
$> 8\,000$	+ by agreement 0^a
^a See option 11.	

Option 12: Another specified length and/or tolerance shall be delivered.


8.5.6 Straightness

The deviation from straightness e of any tube length L measured in accordance with Figure 2 shall not exceed $0,002\,5\,L$ for side lengths ≤ 30 mm and $0,001\,5\,L$ for side lengths > 30 mm.

NOTE In the case of tubes with rectangular cross section, the side length limit applies for the shorter side length.

Deviations from straightness over 1 m length shall not exceed 3 mm, unless option 13 is specified.

Option 13: A reduced maximum deviation from straightness is specified.

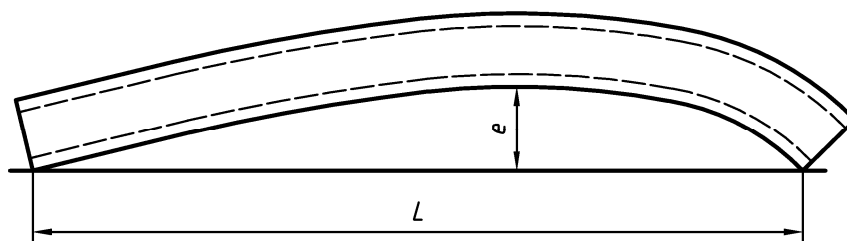


Key

- L tube length
 e deviation from straightness

Figure 2 — Measurement of deviation from straightness e

8.5.7 Squareness of sides

The deviation from squareness of sides, measured as the difference between 90° and θ as shown in Figure 3, shall not exceed $\pm 1^\circ$.

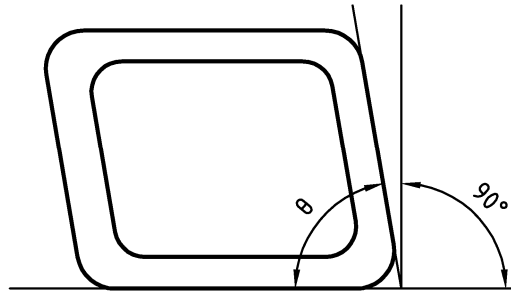

NOTE The deviation from squareness equals to 90° minus θ .

Figure 3 — Squareness of sides


8.5.8 Concavity and convexity

The concavity and convexity is included in the tolerances of B and H .

8.5.9 Twist

The maximum twist V (see Figure 4) shall be:

- a) ≤ 3 mm for B or $H \leq 30$ mm;
- b) $\leq B/10$ or $\leq H/10$ for B or $H > 30$ mm.

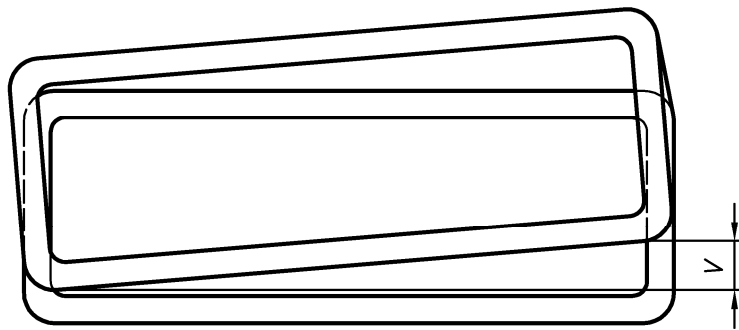

Key

V maximum twist

Figure 4 — Twist

8.5.10 Preparation of ends

Unless option 14 is specified, the tubes shall be delivered with square cut ends. The ends shall be free of excessive burrs.

Option 14: A specified end finishing operation shall be carried out.

9 Inspection

9.1 Types of inspection

The compliance with the requirements of the order shall be checked by non-specific inspection, unless option 15 is specified.

Option 15: *Specific inspection is specified.*

9.2 Inspection documents

9.2.1 Types of inspection documents

In the case of non-specific inspection a test report 2.2 in accordance with EN 10204 shall be issued.

When specific inspection is requested an inspection certificate 3.1 in accordance with EN 10204 shall be issued.

9.2.2 Content of inspection documents

9.2.2.1 The content of the inspection document shall be in accordance with EN 10168 as shown in 9.2.2.2 and 9.2.2.3.

9.2.2.2 For tubes supplied with non-specific inspection the test report 2.2 shall contain the following codes and information:

- A commercial transactions and parties involved;
- B description of products to which the inspection applies;
- C10 to C13 tensile test;
- C60 to C69 other tests;
- C71 to C92 chemical composition;
- D01 marking, surface appearance, shape and dimensional properties;
- Z validation.

9.2.2.3 For tubes supplied with specific inspection the inspection document 3.1 shall contain the following codes and information:

- A commercial transactions and parties involved;
- B description of products to which the inspection applies;
- C01 to C02 the location of samples and orientation of test pieces;
- C10 to C13 tensile test;
- C60 to C69 other tests;
- C71 to C92 chemical composition (cast analysis);
- D01 marking, surface appearance, shape and dimensional properties;
- D02 to D99 other (optional) tests (e.g. roughness measurement, NDT for defects);

Z validation.

9.3 Summary of inspection and testing

Inspection and testing shall be carried out as stated in Table 8 and 10.1.

Table 8 — Summary of inspection and testing

Type of inspection or test		Frequency of testing ^a		Reference
		Non-specific inspection	Specific inspection	
Mandatory	Chemical analysis	M	M	8.2
	Tensile test	M	One per test unit	8.3, 11.1
	Dimensional inspection	M	M	8.5, 11.2
	Visual examination	M	M	11.4
Optional	Roughness measurement (Options 6 and 7)	not applicable	One per test unit	8.4.5, 11.3
	NDT on longitudinal imperfections (Option 8)	not applicable	Each tube	8.4.8, 11.5
^a M: according to manufacturer's procedure.				

10 Sampling

10.1 Frequency of tests

10.1.1 Test unit

A test unit is defined as a quantity of tubes of the same steel grade and dimensions continuously manufactured by the same process and in the same delivery condition heat treated, where applicable, in the same batch and the same heat treatment facility.

NOTE In the case of a continuous heat treatment furnace, a batch is the lot heat treated without intermission with the same process parameters.

A test unit shall comprise not more than 2 t or 3 000 m or 500 tubes or the parent coil for non-heat treated tubes, whichever is the greater mass. Residual quantities of less than 50 tubes may be combined with one or more test unit(s).

Option 16: The test unit shall only contain tubes from one cast.

10.1.2 Number of sample tubes

One sample tube shall be taken from each test unit.

10.2 Preparation of samples and test pieces

10.2.1 General

Samples and test pieces shall be taken at the tube ends and in accordance with EN ISO 377 from one sample tube per test unit.

10.2.2 Test pieces for the tensile test

The test pieces shall be prepared in accordance with EN ISO 6892-1. At the manufacturer's discretion the test piece shall be either a full tube section or a strip section taken in a direction longitudinal to the axis of the tube. Strip sections shall be taken from a side, in case of rectangular tubes from the longer side, excluding the corner profile $C + 5 \text{ mm}$ (see Figure 1) and shall not contain the weld seam.

For thicknesses 3 mm and above proportional or non-proportional test pieces shall be used, the type is at the discretion of the manufacturer. For thicknesses less than 3 mm non-proportional test pieces shall be used. For proportional test pieces the gauge length shall be $L_0 = 5,65 \sqrt{S_0}$ (S_0 = initial cross sectional area of the test piece). The width and gauge length of non-proportional test pieces shall comply with Table 9.

Table 9 — Width and gauge length for non-proportional tensile test pieces

Side length B^a mm	Width of the test piece mm	Gauge length mm
> 35	20	80
$20 \leq B^a \leq 35$	12,5	50
< 20	by agreement	by agreement
^a H for rectangular tubes.		

10.2.3 Test pieces for outside roughness measurement

The test pieces should be taken from the same location as for the mechanical tests.

11 Test methods

11.1 Tensile test

The test shall be carried out at room temperature in accordance with EN ISO 6892-1 and the following determined:

- a) the tensile strength R_m ;
- b) the upper yield strength R_{eH} ;

If a yield phenomenon is not present the 0,2 % proof strength $R_{p0,2}$ or the 0,5 % proof strength (total extension) $R_{t0,5}$ shall be determined. In case of dispute, the 0,2 % proof strength $R_{p0,2}$ shall apply.

- c) the percentage elongation after fracture A shall be reported with reference to a gauge length L_0 of $5,65 \sqrt{S_0}$.

If a non-proportional test piece is used, the percentage elongation value shall be converted to the value for a gauge length $L_0 = 5,65 \sqrt{S_0}$ using the conversion tables given in EN ISO 2566-1.

11.2 Dimensional inspection

The dimensions of the tubes (see Figure 1) shall be checked for compliance with this document. Measurements shall be carried out at a distance of $\geq 100 \text{ mm}$ from the tube ends.

11.3 Roughness measurement

Roughness shall be measured in the axial direction in accordance with EN ISO 4287 outside the weld bead.

11.4 Visual examination

The tubes shall be visually examined for compliance with the requirements of 8.4.1.

11.5 Non-destructive testing

Non-destructive testing for the detection of longitudinal imperfections of the weld shall be carried out at the discretion of the manufacturer, either prior or after sizing and shaping in accordance with one or both of the following methods:

- a) eddy current testing in accordance with EN 10246-3, acceptance level E3 or E3H; and/or
- b) ultrasonic testing in accordance with EN 10246-8, acceptance level U3.

11.6 Retests, sorting and reprocessing

For retests, sorting and reprocessing EN 10021 applies.

12 Marking

The following marking shall, unless option 17 is specified, be shown on a label attached to the package unit or, where necessary for identification, to the single tube:

- a) the manufacturer's name or trade mark;
- b) the specified dimensions;
- c) the number of this European Standard;
- d) the steel name or number;
- e) the delivery condition including the surface condition (symbol);
- f) the cast number, when option 16 applies;
- g) in the case of specific inspection, an identification number (e.g. order or item number) which permits the correlation of the product or delivery unit to the related document.

Option 17: *Alternative marking is specified.*

13 Protection and packaging

The tubes shall be delivered with a temporary corrosion protection. The type of protection shall be at the discretion of the manufacturer, unless option 18 or 19 is specified.

NOTE 1 Resistance to corrosion depends upon the storage condition.

Option 18: *The tubes shall be delivered without corrosion protection.*

Option 19: *The tubes shall be delivered with a specified corrosion protection to be agreed at the time of enquiry and order.*

NOTE 2 Unprotected tubes are prone to corrosion at any stage of storage or transportation.

The tubes shall be delivered bundled, unless option 20 is specified.

Option 20: *Supply of unbundled tubes or application of a specific packaging method is specified.*

Bibliography

- [1] EN 473, *Non-destructive testing — Qualification and certification of NDT personnel — General principles*
- [2] EN ISO 1461, *Hot dip galvanized coatings on fabricated iron and steel articles — Specifications and test methods (ISO 1461:2009)*